

Monte Carlo simulations of magnetovolume instabilities in anti-Invar systems

M.E. Gruner and P. Entel

Theoretische Tieftemperaturphysik

Gerhard-Mercator-Universität – GH Duisburg, D-47048 Duisburg, Germany

Tel.: +49-203-379-3564, Fax.: +49-203-379-2965, eMail: me@thp.Uni-Duisburg.DE

Presented at ICAM '97 / E-MRS spring meeting, Strasbourg, France, 1997

Abstract

We perform constant pressure Monte Carlo simulations of a spin-analogous model which describes coupled spatial and magnetic degrees of freedom on an fcc lattice. Our calculations qualitatively reproduce magnetovolume effects observed in some rare earth manganese compounds, especially in the anti-Invar material YMn_2 . These are a sudden collapse of the magnetic moment which is connected with a huge volume change, and a largely enhanced thermal expansion coefficient.

INTRODUCTION

The observation that some transition metal alloys and complexes have an anomalously low or high thermal expansion coefficient is widely referred to as the Invar or anti-Invar effect, respectively. Since the discovery of Fe-Ni Invar one century ago, uncounted investigations in this topic have taken place (for recent reviews see [1]). A major advance has been achieved by ab initio band structure calculations (e. g. [2, 3]). KKR-CPA calculations of $\text{Fe}_{65}\text{Ni}_{35}$ [3] reveal two nearly degenerate minima on the binding surface, i.e. the energy as a function of lattice constant and mean magnetic moment. One at a large lattice constant and a large magnetic moment (high moment or HM state) and another at a smaller lattice constant and a smaller or vanishing magnetic moment (low moment or LM state). In this case, thermal excitation of the LM state can lead to a compensation of the volume expansion of the material. This scenario reminds of the phenomenological 2- γ -states model [4] introduced by Weiss in order to explain Fe-Ni Invar. However, most ab initio calculations are performed for zero temperature only. So the comparison with experimental data is hampered by the fact that the extrapolation of these results to finite temperatures is connected with severe methodological problems. So far mainly continuous Ginzburg Landau like spin models in combination with a Gaussian fluctuation theory have been used to achieve this goal [5]. Another approach is to use a Weiss-type model with its parameters adapted to ab initio results. This has been done for the classical Invar system Fe-Ni, and although we neglected the itinerant character of magnetism by using localized spins, we were able to reproduce qualitatively the major magnetovolume effects of this alloy [6].

However, it has still to be proven, whether this approach can be applied to other materials, especially to anti-Invar systems. One of the most prominent anti-Invar materials is the Laves phase compound YMn_2 . It occurs in the C15 structure with a frustrated antiferromagnetic (AF) spin order in the Mn sublattice. Around $T_N \approx 100$ K YMn_2 undergoes a first order phase transition into a paramagnetic state, accompanied by a huge volume contraction of 5 % and a large thermal hysteresis of 30 K. Above T_N a large thermal expansion coefficient of $50 \times 10^{-6} \text{ K}^{-1}$ is encountered [7]. LMTO calculations reveal a nonmagnetic solution at a lower volume with a slightly higher energy than the AF ground state [8].

Within the scope of this work, we will show that for a suitable choice of parameters the large abrupt volume change at T_N as well as the enhanced thermal expansion of YMn_2 can be qualitatively reproduced by a Weiss type model assuming a HM-LM instability of the Mn atom.

THE MODEL

Our model Hamiltonian consists of a magnetic part H_m describing the magnetic properties of the system and a vibrational part H_v responsible for the magnetovolume coupling:

$$H = \underbrace{D \sum_i S_i^2 + J \sum_{\langle i,k \rangle} S_i S_k}_{H_m} + \underbrace{\sum_{\langle i,k \rangle} U(r_{ik}, S_i, S_k)}_{H_v} . \quad (1)$$

H_m is a spin-1 Ising Hamiltonian, also known as Blume-Capel model. We identify the spin states $S_i = 0$ with the atomic LM state, whereas $S_i = \pm 1$ refers to the HM state. D denotes the crystal field, which imposes an energetic separation between HM and LM states; J is the magnetic exchange constant. The brackets indicate a summation over nearest neighbors. We did not consider a distance dependence of J so far, since we believe its influence to be small compared to the effect observed. Furthermore, compressible frustrated Ising antiferromagnets show additional effects like tetragonal lattice distortions [9], that are not covered by experimental data in our case. The second part H_v introduces pair interactions between the atoms, which depend on their distance r_{ik} and on their spin states. If both of the interacting atoms are in the HM state, we employ HM potentials that are characterized by a larger equilibrium distance than the LM potentials we use otherwise. So a system with a considerable concentration of LM atoms is supposed to have a smaller lattice constant than a pure HM system. For the sake of simplicity we choose Lennard-Jones interactions:

$$U(r_{ik}, S_i, S_k) = \begin{cases} 4\epsilon_L \left(\left(\frac{d_L}{r_{ik}} \right)^{12} - \left(\frac{d_L}{r_{ik}} \right)^6 \right), & S_i S_k = 0 \\ 4\epsilon_H \left(\left(\frac{d_H}{r_{ik}} \right)^{12} - \left(\frac{d_H}{r_{ik}} \right)^6 \right), & S_i S_k \neq 0 \end{cases}, \quad (2)$$

where $\epsilon_{L,H}$ denote the energy at the equilibrium neighbor distances $r_{ik} = 2^{1/6} d_{L,H}$ for LM and HM potentials, respectively.

THE SIMULATION

Our Monte Carlo routine consists of two local and one global update steps. For each lattice site we choose a new spin state $S_i \in \{0, \pm 1\}$ using the Metropolis criterion. Afterwards a new trial position is elected out of a cube around the old position. Again, the new position is accepted with the probability $\max(1, \exp(-\beta \Delta H))$, where β is the inverse temperature. The size of the cube is given by the condition that about half of the propositions are to be accepted in order to improve convergence. When all atoms have been updated, the volume of the complete lattice is adapted by another Metropolis step, except that now the quantity $\Delta \mathcal{H} = \Delta H - N k_B T \ln(V'/V)$ has to be considered, which accounts for the difference in translational entropy caused by the change of the volume from V to V' (for more information on constant pressure Monte Carlo methods see [10]). Our calculations were performed on a $8^3 \times 4 = 2048$ site fcc lattice with periodic boundary conditions at constant pressure $P = 0$. 80 000 lattice sweeps were performed for each temperature. The first 40 000 lattice sweeps were used to allow the system to reach equilibrium, afterwards every tenth sweep data were gathered for the statistics.

Although YMn_2 occurs in the C15 structure, we chose instead an fcc lattice in our simulations. This allows us to omit the Y species, which we do not expect to play an important role in the thermodynamics of the HM-LM transition. Furthermore we can easily relate our results to previous investigations [6]. Since the fcc Ising antiferromagnet has also a frustrated ground state spin structure as it is assumed for YMn_2 , simulating an fcc structure is not a serious restriction. We used $d_H = 2.432 \text{ \AA}$ and $d_L = 2.397 \text{ \AA}$ for the interatomic spacing between the Mn atoms in AF and paramagnetic YMn_2 . We chose $\epsilon_L = \epsilon_H = 30.86 \text{ mRy}$ in order to achieve a reasonable elastic behavior. The exchange constant was set to $J = 0.459 \text{ mRy}$ corresponding to a Néel temperature $T_N = 126.5 \text{ K}$ [11]. The crystal field D was varied in the range $D = 0 \dots 3 J$. We examined the energy per lattice site $\langle e \rangle$, the mean magnetic moment $\langle S^2 \rangle = \langle 1/N \sum_i S_i^2 \rangle$, the atomic volume $\langle V \rangle$ and the linear thermal expansion coefficient $\alpha = 1/(3V) dV/dT$ (brackets denote thermal averaging). Additionally, for several values of D , we approximated ground state energy and average magnetic moment as a function of the lattice constant by exponentially cooling down the system to $T = 4 \text{ K}$ at constant volume.

RESULTS

For $D < 2J$, the ground state of the system is an AF HM state as can be seen from simple energetic considerations concerning Hamiltonian (1). Correspondingly, for $D > 2J$, the ground state turns into a nonmagnetic LM state with a smaller volume. This is also verified by the plots of low temperature energy and magnetic moment vs. lattice constant shown in Fig. 1.

Disallowing the LM spin state ($D = -\infty$), around $T_N = 127$ K a first order phase transition occurs from a type 1 AF state to a paramagnetic state. This transition can be observed as a finite jump in the energy per lattice site (Fig. 2). Enlarging D allows thermal excitations of the $S = 0$ spin state, leading initially to a continuous decrease of HM atoms with increasing temperature, which appears in our results for $D = 0$ (Fig. 3). Due to the magnetovolume coupling introduced by H_v , this is connected with a continuous decrease of the volume and, correspondingly, a reduction of the thermal expansion coefficient, as depicted by Fig. 4. The AF phase transition is hardly affected by the dilution of the magnetic system and remains of first order; only T_N is slightly reduced. We now find a finite jump in $\langle e \rangle$ at $T_N = 124$ K. An investigation of the probability distribution (not shown) of the internal energy at T_N exhibits the two maxima structure that is typical for first order phase transitions.

For $D = J$, we find a sudden collapse of the magnetic moment at $T_s = 127$ K which is connected with an abrupt decrease of the volume of about 3 %. The magnetic phase transition takes place a few Kelvin below at $T_N = 120$ K. This situation is reflected in a double jump of the internal energy. Upon cooling down, a large thermal hysteresis is encountered: The system has to be cooled down to $T'_N = 53$ K before it jumps back into the AF HM state. Responsible for this hysteresis is that lattice strain imposes a large free energy barrier between HM and LM states which is unlikely to be surmounted by our constant pressure Monte Carlo algorithm. However, the large energy barrier is suppressed in Fig. 1, since at constant volume the system is forced into a mixture of two coexisting HM and LM phases. Similar first order transitions with a large thermal hysteresis have also been observed in simulations of ferromagnetic systems; for a detailed discussion we refer to [6]. Above T_s the mean magnetic moment is considerably lower than the high temperature limit $\langle S^2 \rangle = 2/3$ of a spin-1 Ising model. So with increasing temperature more atoms will be excited to the HM state, leading to an enhanced thermal expansion. This process is further encouraged with increasing temperature, because the displacement of the atoms due to lattice vibrations and the difference between HM and LM neighbor distances become comparable. This levels out the energetic difference between $S_i = 0$ and $S_i = \pm 1$ states introduced by H_v . For the same reason, discontinuous magnetovolume effects do not occur for smaller values of D : At higher temperatures, the HM and LM minima of the free energy are smeared out by lattice vibrations.

Above $D = 2J$, the ground state of the system is nonmagnetic. So HM-LM transitions as well as magnetic phase transitions do not appear. However, we observe an enhanced thermal expansion coefficient, due to excitation of HM atoms.

DISCUSSION

For $D = J$, our model shows magnetovolume effects similar to the properties of YMn_2 mentioned in the introduction: An abrupt collapse of the mean magnetic moment connected with a decrease of the volume of several percent and a largely enhanced thermal expansion coefficient. Lowering D produces continuous magnetovolume effects. This resembles the situation in $\text{Y}(\text{Mn}_{1-x}\text{Al}_x)_2$, where small concentrations of Al destroy the first order transition and anti-Invar behavior [12]. With increasing Al content the magnetovolume effects gradually vanish. This is due to the enlargement of the lattice constant by the Al atoms which makes it energetically more difficult for the Mn atoms to switch to the LM state. On the other hand, substituting a few percent of the Y atoms with the smaller Sc has the opposite effect: The Mn atoms are nonmagnetic at $T = 0$, the Mn moment increases with temperature, leading to an enhanced thermal expansion coefficient [13]. This is the situation we observed for $D > 2J$.

Acknowledgments

This work has been supported by the Deutsche Forschungsgemeinschaft through the SFB 166. We also thank the HLRZ (KFA Jülich) since part of the work was done on their PARAGON parallel computer.

REFERENCES

- [1] E.F. Wassermann, in *Ferromagnetic Materials* Vol. 5 edited by K. H. J. Buschow and E. P. Wohlfarth, p. 237, Amsterdam, Elsevier 1990. M. Shiga, in *Materials Science and Technology*, Vol. 3B edited by R.W. Cahn, P. Haasen, E.J. Kramer, p. 159, Weinheim, VCH 1994.
- [2] P. Entel, E. Hoffmann, P. Mohn, K. Schwarz, V.L. Moruzzi, Phys. Rev. B **47**, 8706 (1993). E. Hoffmann, P. Entel, K. Schwarz, P. Mohn, J. Magn. Magn. Mater. **140-144**, 237 (1995).
- [3] M. Schröter, H. Ebert, H. Akai, P. Entel, E. Hoffmann, G.G. Reddy, Phys. Rev. B **52**, 188 (1995).
- [4] R.J. Weiss, Proc. Roy. Phys. Soc. (London) **82**, 281 (1963).
- [5] P. Mohn, K. Schwarz, D. Wagner, Phys. Rev. B **43**, 3318 (1991); M. Uhl, J. Kübler, Phys. Rev. Lett. **77**, 334 (1996); and references herein.
- [6] M.E. Gruner, R. Meyer, P. Entel, submitted to Z. Phys. B.
- [7] M. Shiga, Physica B **149**, 293 (1988); R. Ballou, J. Deportes, R. Lemaire, Y. Nakamura, B. Oulad-diaf, J. Magn. Magn. Mater. **70**, 129 (1987); and references herein.
- [8] S. Asano, S. Ishida, J. Magn. Magn. Mater. **70** 39 (1987).
- [9] L. Gu, B. Chakraborty, P.L. Garrido, M. Phani, J.L. Lebowitz, Phys. Rev. B **53**, 11985 (1996).
- [10] M.P. Allen, D.J. Tildesley, *Computer Simulation of Liquids*, Oxford, Clarendon 1987.
- [11] D.F. Styer, Phys. Rev. B **32**, 393 (1985).
- [12] M. Shiga, H. Wada, H. Nakamura, K. Yoshimura, Y. Nakamura, J. Phys. F **17**, 1781 (1987).
- [13] M. Shiga, H. Wada, Y. Nakamura, J. Deportes, B. Oulad-diaf, K.R.A. Ziebeck, J. Phys. Soc. Jpn. **57**, 3141 (1988).

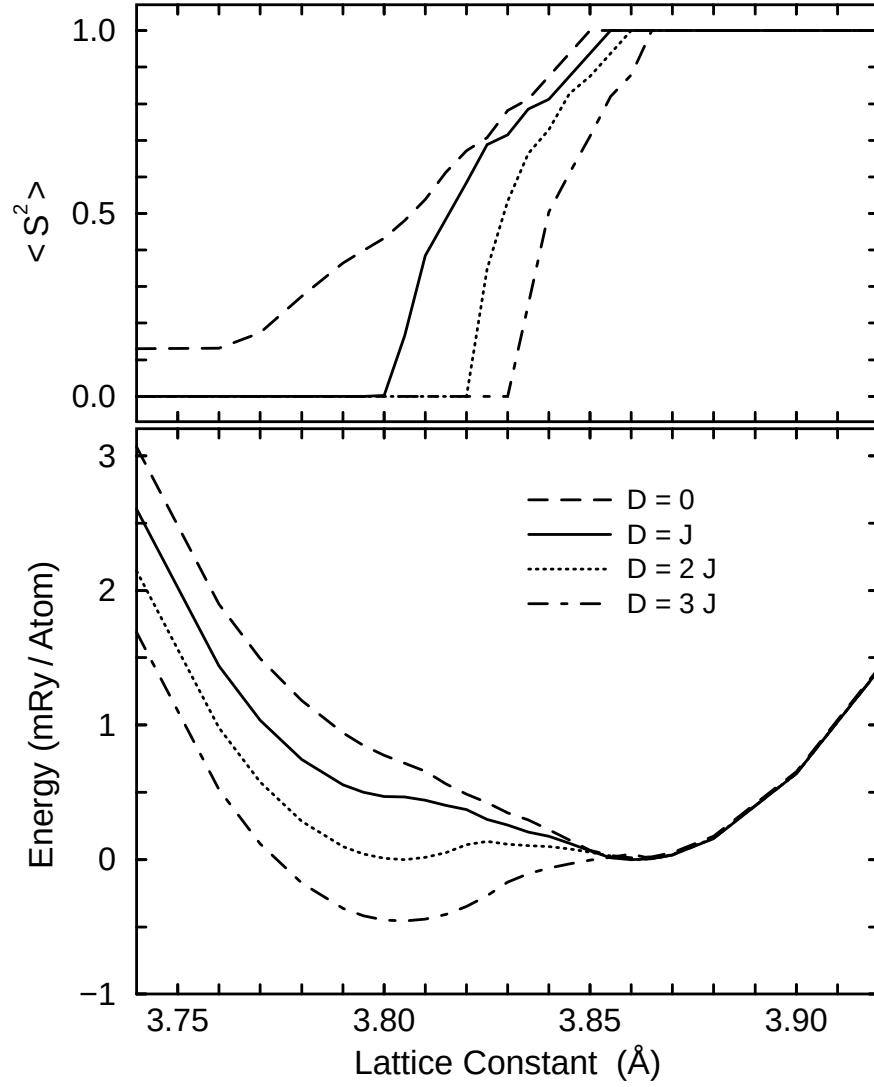


Figure 1: Energy per lattice site and average magnetic moment at $T = 4$ K as a function of the lattice constant.

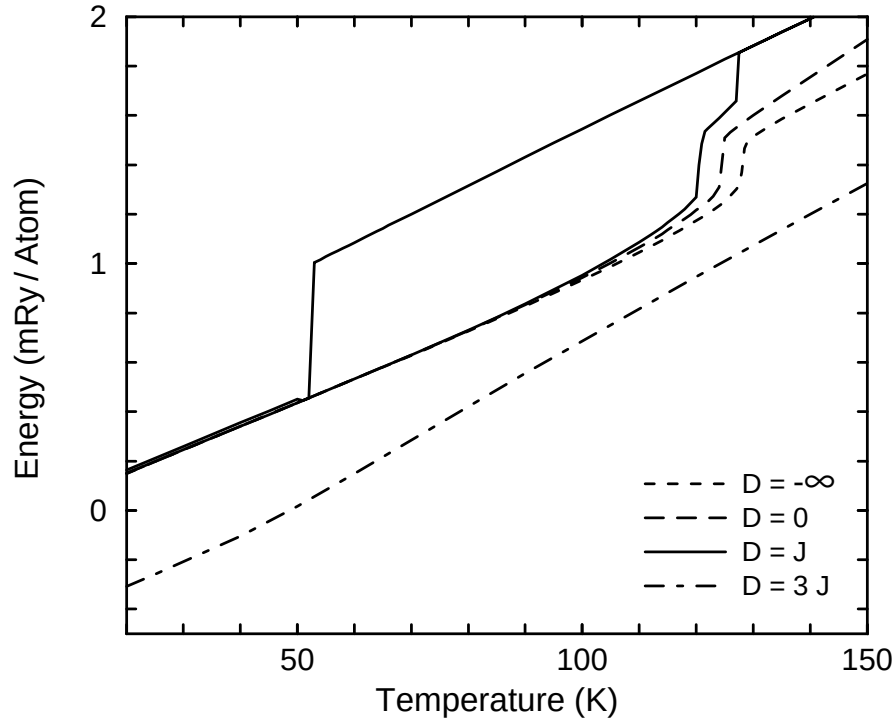


Figure 2: Energy per lattice site for various values of D as a function of the temperature.

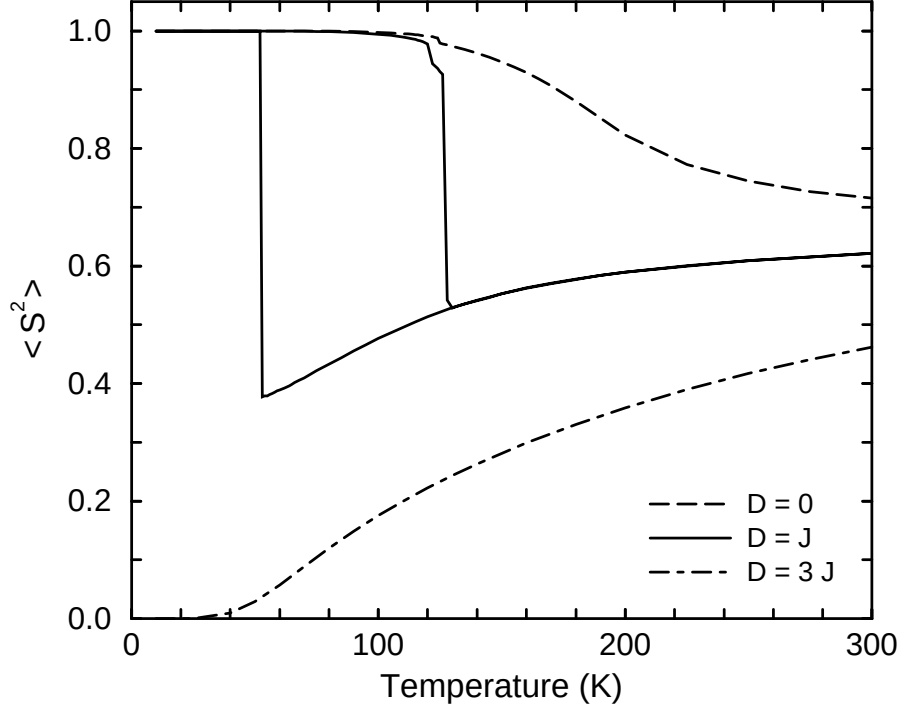


Figure 3: Temperature dependence of the average magnetic moment for various values of D .

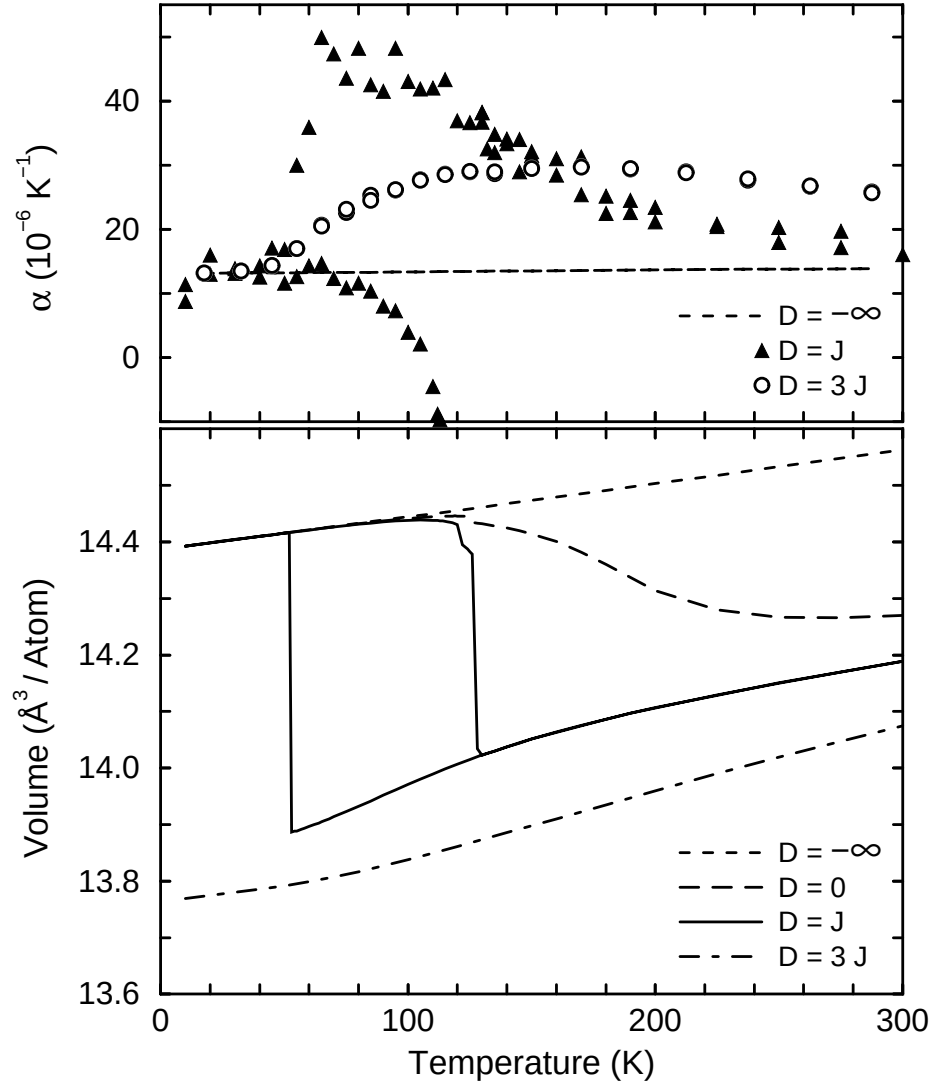


Figure 4: Temperature dependence of the volume and the linear thermal expansion coefficient for various values of D .